

---

---

# ***Louisiana Transportation Research Center***

---

---

Technical Assistance Report 19-01 TA-B

## **Variability of In-Line RAP Crushing vs. Pre-Screened Stockpiles**

by

Corey Mayeux, P.E.  
Saman Salari, P.E.  
Samuel Cooper, III, Ph.D., P.E.

***LTRC***

---

---



4101 Gourrier Avenue | Baton Rouge, Louisiana 70808  
(225) 767-9131 | (225) 767-9108 fax | [www.ltrc.lsu.edu](http://www.ltrc.lsu.edu)

## TECHNICAL REPORT STANDARD PAGE

---

1. Title and Subtitle  
**Variability of In-Line RAP Crushing vs. Pre-Screened RAP Stockpiles**
2. Author(s)  
Corey Mayeux, P.E., Saman Salari, P.E., and Samuel Cooper, III, Ph.D., P.E.
3. Performing Organization Name and Address  
Louisiana Transportation Research Center  
4101 Gourrier Avenue  
Baton Rouge, LA 70808
4. Sponsoring Agency Name and Address  
Louisiana Department of Transportation and Development  
P.O. Box 94245  
Baton Rouge, LA 70804-9245
5. Report No.  
**FHWA/LA.17/19-01TA-B**
6. Report Date  
November 2019
7. Performing Organization Code  
LTRC Project Number: 19-01TA-B
8. Type of Report and Period Covered  
Technical Assistance Final Report  
8/19-10/19
9. No. of Pages  
17
10. Supplementary Notes  
Conducted in Cooperation with the U.S. Department of Transportation, Federal Highway Administration
11. Distribution Statement  
Unrestricted. This document is available through the National Technical Information Service, Springfield, VA 21161.
12. Key Words  
Reclaimed Asphalt Pavement; RAP; Variability; Properties
13. Abstract  
The Louisiana Department of Transportation and Development (DOTD) allows contractors to utilize RAP in various asphalt mixtures throughout the state. The standard specifications for roads and bridges added the following statement regarding the storing of RAP, “Keep reclaimed asphalt pavement separate from other materials at the plant in such a manner that will allow for Department inspection and acceptance. Keep stockpiles uniform and free of soil, debris, foreign matter and other contaminants. Screen or crush RAP, prior to use, to pass a 1-inch sieve.” The wording of this statement has led contractors to stockpile RAP in two different manners; contractors crush and screen the RAP prior to stockpiling, or they store the RAP then crush and screen it on the cold feed line. LTRC was requested to evaluate the variability of RAP properties with respect to these storage methods.

# **Variability of In-Line RAP Crushing vs. Pre-Screened RAP Stockpiles**

By

Corey Mayeux, P.E.  
Asphalt Research Engineer

Saman Salari, P.E.  
Asphalt Research Engineer

Samuel Cooper, III, Ph.D., P.E.  
Materials Research Administrator

Louisiana Transportation Research Center  
4101 Gourrier Avenue  
Baton Rouge, LA 70808

LTRC Project No. 19-01TA-B

conducted for

Louisiana Department of Transportation and Development  
Louisiana Transportation Research Center

The contents of this report reflect the views of the author/principal investigator who is responsible for the facts and the accuracy of the data presented herein.

The contents of do not necessarily reflect the views or policies of the Louisiana Department of Transportation and Development, the Federal Highway Administration or the Louisiana Transportation Research Center. This report does not constitute a standard, specification, or regulation.

November 2019

## **Abstract**

The Louisiana Department of Transportation and Development (DOTD) allows contractors to utilize RAP in various asphalt mixtures throughout the state. The standard specifications for roads and bridges added the following statement regarding the storing of RAP, “Keep reclaimed asphalt pavement separate from other materials at the plant in such a manner that will allow for Department inspection and acceptance. Keep stockpiles uniform and free of soil, debris, foreign matter and other contaminants. Screen or crush RAP, prior to use, to pass a 1-inch sieve.” The wording of this statement has led contractors to stockpile RAP in two different manners; contractors crush and screen the RAP prior to stockpiling, or they store the RAP then crush and screen it on the cold feed line. LTRC was requested to evaluate the variability of RAP properties with respect to these storage methods.

# Table of Contents

Technical Report Standard Page .....	1
Variability of In-Line RAP Crushing vs. Pre-Screened RAP Stockpiles .....	2
Abstract .....	3
Table of Contents .....	4
List of Tables .....	5
List of Figures .....	6
Introduction .....	7
Objective .....	8
Scope .....	9
Methodology .....	10
Discussion of Results .....	11
Sieve Analysis of Fine and Coarse Aggregates .....	11
Quantitative Extraction of Asphalt Binder from HMA .....	13
Theoretical Maximum Specific Gravity ( $G_{mm}$ ) .....	14
Bulk Specific Gravity ( $G_{sb}$ ) .....	15
Conclusions .....	16
Recommendations .....	17

## List of Tables

Table 1. Standard Deviation of Percent Passing .....	12
Table 2. Coefficient of Variance of Percent Passing .....	13
Table 3. Asphalt Content of RAP Samples .....	13
Table 4. Maximum Specific Gravity Results .....	14
Table 5. Bulk Specific Gravity Results .....	15

## List of Figures

Figure 1. In-Line RAP Gradation .....	11
Figure 2. Pre-Screened RAP Gradation .....	12

## Introduction

When an asphalt roadway undergoes rehabilitation or reconstruction, the old pavement may be reclaimed for use in hot mix asphalt production. This material, commonly referred to as Reclaimed Asphalt Pavement (RAP), is one of the most recycled materials in the United States. DOTD's *Standard Specifications for Roads and Bridges* allows RAP to be used, but contractors must screen or crush RAP to pass a 1-inch sieve prior to use. Asphalt contractors meet this criterion via two different methods. They crush and screen the RAP prior to stockpiling or they store the RAP then crush and screen it on the cold feed line. LTRC personnel has obtained a RAP sample from two different asphalt contractors; Diamond B Construction crushes its RAP to size prior to stockpiling it, and Prairie Contractors stockpiles uncrushed RAP and crushes it down to size with an in-line crusher on the cold feed line. Testing and analysis of these samples was used to determine if these varying methods of storing the RAP has an influence on its properties.



## **Objective**

The objective of this technical assistance was to evaluate the variability in RAP that is crushed and screened prior to being stockpiled versus the variability in RAP that is crushed and screened on the cold feed line.

## Scope

LTRC personnel obtained a total of two RAP samples from two contractors. The samples were transferred to the LTRC asphalt laboratory and split in to three replicates from each source. Qualified technicians then ran a variety of asphalt mixture tests, which included the following:

- Standard Method of Test for Mechanical Analysis of Extracted Aggregate (AASHTO T 30)
- Standard Method of Test for Specific Gravity and Absorption of Fine Aggregate (AASHTO T 84)
- Standard Method of Test for Specific Gravity and Absorption of Coarse Aggregate (AASHTO T 85)
- Standard Method of Test for Theoretical Maximum Specific Gravity (ASHTO T 209)
- Standard Method of Test for Determining the Asphalt Binder Content of Hot Mix Asphalt (HMA) by the Ignition Method (AASHTO T 308)
- Standard Test Method for Automated Extraction of Asphalt Binder from Asphalt Mixtures (ASTM D8159)

## Methodology

A suite of tests was conducted to determine the level of variance in the RAP samples.

- Sieve analysis of Fine and Coarse Aggregates, AASHTO T 30, was used to compare the gradations of the two RAP samples.
- Standard Method of Test for Determining the Asphalt Binder Content of Hot Mix Asphalt (HMA) by the Ignition Method, AASHTO T 308, was used to determine the asphalt binder content of the RAP samples.
- Standard Test Method for Automated Extraction of Asphalt Binder from Asphalt Mixtures (ASTM D8159) was performed to calculate the asphalt binder content.
- Mixture Maximum Specific Gravity ( $G_{mm}$ ) was determined according to AASHTO T 209. Specific Gravity and Absorption of Fine & Coarse Aggregate ( $G_{sb}$ ) was determined according to AASHTO T 84 and AASHTO T 85. The variability of the aforementioned properties was compared using the standard deviation of the three replicates tested.

# Discussion of Results

## Sieve Analysis of Fine and Coarse Aggregates

Prior to sieve analysis, an infraTest asphalt analyzer (ASTM D8159) was used to extract the asphalt binder from the aggregate for each of the RAP samples. In addition to the infraTest extractions, the Ignition Method (AASHTO T 308) for extraction was also conducted on each of the RAP samples.

After extraction, a sieve analysis was conducted in accordance with AASHTO T 30. The sieve analysis results for the In-Line RAP samples are shown in Figure 1 and results for the Pre-Screened RAP samples are shown in Figure 2. The gradation results from the infraTest asphalt analyzer samples are labelled 'Extraction' while results from the Ignition method are labelled 'Burn.'

Figure 1 displays the average percent passing for the burn and extracted In-Line RAP samples. The chart shows that the two samples are similarly graded.

Figure 1. In-Line RAP Gradation


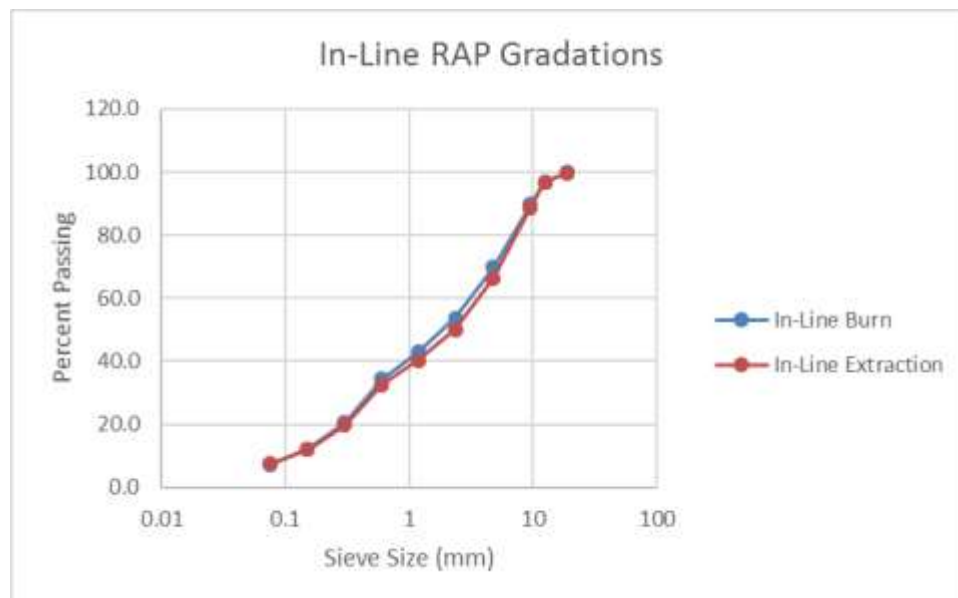


Figure 2 displays the average percent passing for the burn and extracted Pre-Screened RAP samples. The chart shows that the two samples are similarly graded.

**Figure 2. Pre-Screened RAP Gradation**

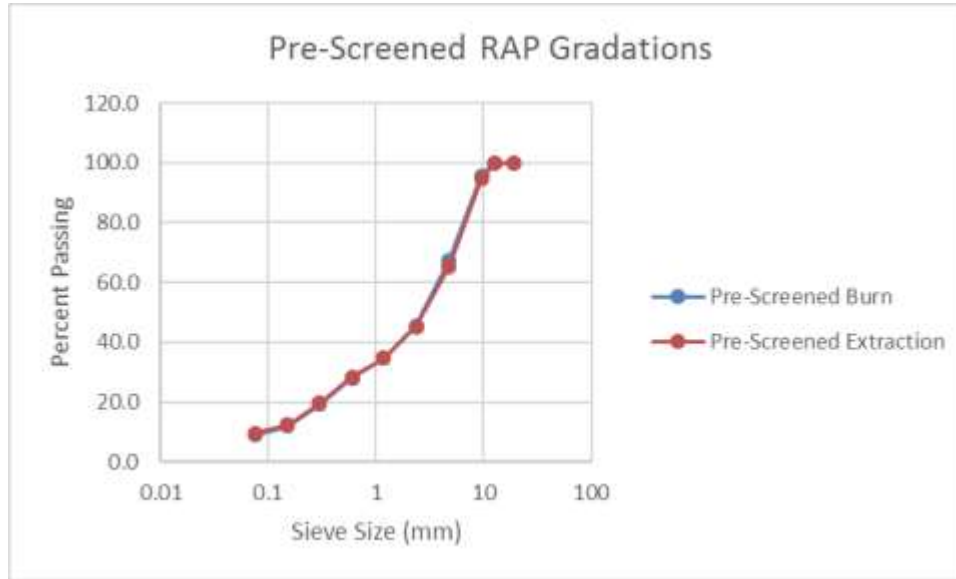

The standard deviation of the three test samples was determined for each sieve size to determine if there was significant variability. The standard deviations can be seen in Table 1 below and the coefficient of variance is reported in Table 2. It can be seen that the In-Line resulted in a lower average variability for the gradations. It should also be noted that the extracted Pre-Screened sample had higher standard deviations on sieve sizes 2.36 mm and 1.18 mm; these deviations fall outside of the  $\pm 3$  and  $\pm 2$  tolerance allowed in the asphalt specifications. Additionally, the coefficient of variance is lower for the In-Line data.

**Table 1. Standard Deviation of Percent Passing**

Mixture	Method	Sieve Opening (mm)										
		19	12.5	9.5	4.75	2.36	1.18	0.6	0.3	0.15	0.075	Avg
<b>Burn</b>	<b>In-Line</b>	0.00	0.75	1.07	0.72	0.71	0.66	0.51	0.21	0.12	0.17	0.49
	<b>Pre-Screened</b>	0.00	0.21	0.71	1.66	1.61	1.25	0.93	0.51	0.25	0.17	0.73
<b>Extraction</b>	<b>In-Line</b>	0.40	0.98	1.24	1.42	0.81	0.49	0.44	0.35	0.23	0.18	0.65
	<b>Pre-Screened</b>	0.00	0.17	0.87	2.76	3.36	2.77	1.59	0.81	0.44	0.35	1.31

**Table 2. Coefficient of Variance of Percent Passing**

Mixture	Method	Sieve Opening (mm)										
		19	12.5	9.5	4.75	2.36	1.18	0.6	0.3	0.15	0.075	Avg
<b>Burn</b>	<b>In-Line</b>	0.00	0.78	1.19	1.03	1.32	1.52	1.49	1.01	0.94	2.44	1.17
	<b>Pre-Screened</b>	0.00	0.21	0.74	2.47	3.52	3.60	3.32	2.67	2.09	1.95	2.06
<b>Extraction</b>	<b>In-Line</b>	0.41	1.02	1.40	2.14	1.62	1.23	1.34	1.76	1.92	2.33	1.52
	<b>Pre-Screened</b>	0.00	0.17	0.91	4.23	7.46	8.01	5.58	4.11	3.49	3.61	3.76

### **Quantitative Extraction of Asphalt Binder from HMA**

The asphalt binder content (%AC) was determined according to AASHTO T 308 in addition to ASTM D8159. The results are presented in Table 3 below. The standard deviation for both Pre-Screened samples is higher than AASHTO allowable standard deviation of 0.069. The standard deviation for the burned In-Line sample is within the AASHTO limit, while the extracted In-Line sample is slightly above the allowed tolerance. Additionally, the In-Line coefficient of variance is lower than the Pre-Screened for each method of asphalt extraction.

**Table 3. Asphalt Content of RAP Samples**

Mixture	Method	Specimen	%AC
<b>Burn</b>	<b>In-Line</b>	<b>1</b>	<b>7.63</b>
		<b>2</b>	<b>7.62</b>
		<b>3</b>	<b>7.60</b>
		<b>Avg</b>	<b>7.62</b>
		<b>Stdev</b>	<b>0.02</b>
		<b>CV (%)</b>	<b>0.20</b>
	<b>Pre-Screened</b>	<b>1</b>	<b>5.78</b>
		<b>2</b>	<b>5.96</b>
		<b>3</b>	<b>5.91</b>
		<b>Avg</b>	<b>5.88</b>

Mixture	Method	Specimen	%AC
		<b>Stdev</b>	<b>0.09</b>
		<b>CV (%)</b>	<b>1.58</b>
Extraction	In-Line	<b>1</b>	<b>5.21</b>
		<b>2</b>	<b>5.15</b>
		<b>3</b>	<b>5.29</b>
		<b>Avg</b>	<b>5.22</b>
		<b>Stdev</b>	<b>0.07</b>
		<b>CV (%)</b>	<b>1.35</b>
	Pre-Screened	<b>1</b>	<b>4.93</b>
		<b>2</b>	<b>5.16</b>
		<b>3</b>	<b>4.92</b>
		<b>Avg</b>	<b>5.00</b>
		<b>Stdev</b>	<b>0.14</b>
		<b>CV (%)</b>	<b>2.71</b>

### Theoretical Maximum Specific Gravity ( $G_{mm}$ )

The Maximum Specific Gravity was determined for each sample set according to AASHTO T 209. The results can be seen in Table 4 below. The pre-screened sample set has a lower standard deviation and coefficient of variance; however, the standard deviation for both sample sets is below the limit of 0.0051 allowed by AASTHO.

**Table 4. Maximum Specific Gravity Results**

Mixture	1	2	3	Avg	Stdev	CV (%)
In-Line	2.436	2.433	2.431	2.433	0.003	0.10
Pre-Screened	2.412	2.411	2.413	2.412	0.001	0.04

## Bulk Specific Gravity ( $G_{sb}$ )

The Bulk Specific Gravity for the fine and coarse aggregates was determined according to AASHTO T 84 and T 85. The results can be seen in Table 5 below. The standard deviation for the In-Line set is lower than Pre-Screened set. The standard deviation for the coarse sample set and the fine In-Line sample is below the limit of 0.011 allowed by AASTHO. The In-Line data also has a lower coefficient of variance for each aggregate type.

**Table 5. Bulk Specific Gravity Results**

Agg. Type	Mixture	1	2	3	Avg	Stdev	CV (%)
Coarse	In-Line	2.485	2.489	2.495	2.490	0.005	0.20
	Pre-Screened	2.449	2.455	2.435	2.446	0.010	0.42
Fine	In-Line	2.508	2.519	2.512	2.513	0.006	0.23
	Pre-Screened	2.474	2.472	2.441	2.463	0.018	0.75



## Conclusions

Two RAP samples were obtained to determine if crushing and pre-screening prior to storage or crushing RAP with an in-line crusher has an influence on its properties. Based on the findings LTRC has determined the following:

- Sieve analysis showed that the In-Line crushed RAP gradations had lower standard deviations than the pre-screened RAP gradations. The extracted Pre-Screened standard deviation for sieve sizes 2.36 mm and 1.18 mm were outside of the tolerance allowed in the asphalt specifications.
- The standard deviation of the asphalt content for the burn and extraction In-Line crushed samples was lower than that of the pre-screened samples. The standard deviation was above the limit allowed by AASHTO for all samples except the burned In-Line sample.
- The standard deviation of the maximum specific gravity was lower for the pre-screened samples. The standard deviation for both sample sets was below the AASHTO limit.
- The standard deviation of the bulk specific gravity was lower for the In-Line samples for both the coarse and fine aggregate types. The standard deviation of the fine aggregate Pre-Screened sample was above the AASHTO tolerance.

## **Recommendations**

Based on the findings, LTRC does not recommend changes be made to the specification to require or disallow either methodology.

This public document is published at a total cost of \$250. 42 copies of this public document were published in this first printing at a cost of \$250. The total cost of all printings of this document including reprints is \$250. This document was published by Louisiana Transportation Research Center to report and publish research findings as required in R.S. 48:105. This material was duplicated in accordance with standards for printing by state agencies established pursuant to R.S. 43:31. Printing of this material was purchased in accordance with the provisions of Title 43 of the Louisiana Revised Statutes.